## Utilization of Blast Furnace Slag in Briquette Production

Baris Sayin and Özlem Çelik Sola

Abstract— The main purpose of this study is to investigate the utilization of blast furnace slag (BFS) in the production of briquettes as a replacement of soil (S). To achieve this first, some physical properties of the materials used were determined. Thermal properties of the materials were examined by using differential thermal analysis- thermo gravimetric analysis (DTA-TG). Following the characterization of the materials, the samples of briquettes made with BFS. Its replacement ratios with soil were 0, 2, 5, 10, 20% in mass basis (w/w). The mixtures were prepared and sintered at 900°C in the furnace. Compressive strength tests results were presented. It can be said that BFS affected sintering behavior of the briquettes. Compressive strength results of the briquette samples indicated that BFS containing briquettes with 39.4MPa compressive strength (No#2), which was higher than the requirements of Turkish Standard Specification (TS EN 771-1) and it was also higher reference mixture's (No#1).

 ${\it Keywords} {\it --} {\it blast} \quad {\it furnace} \quad {\it slag}, \quad {\it compressive} \quad {\it strength}, \\ {\it briquette}$ 

### 1. Introduction

There are many industrial wastes which are used in construction industry [1-7]. One of them is BFS has been used as a mineral additive in the cement and concrete production. It has been used to evaluate and prevent the environmental pollution. Besides it has been contribute decreasing of using of natural resources. BFS is also used ceramic production, but it is rarely used to briquette production. This study investigates to utilize BFS in briquette production that has high compressive strength values.

## п. Experimental

### A. Raw Materials

The materials used in this work were S, supplied from a brick factory in Turkey, BFS was obtained from Iskenderun Iron-Steel Factory. Before the preparation of the specimens from the soil produced with these materials, chemical and some physical analysis of materials were carried out.

Baris Sayin, *Ph.D*Department of Construction and Technical Affairs / Istanbul University Turkey

Özlem Çelik Sola, *Assoc. Prof. Dr.* Department of Civil Engineering / Istanbul University Turkey To obtain particle size distribution, sieve analysis were performed (Fig.1), to determine thermal behavior of S TG analysis was performed (Fig.2).

### B. Preparation and testing of briquettes

Different mixtures were prepared from BFS samples. Briquette dimensions were chosen as  $3.6 \times 3.6 \text{cm}^2$  diameter and height. The mould was made from stainless steel. BFS was added to the soil in ratio of 2, 5, 10, 20% in mass basis (w/w) and mixtures were prepared with 6% water. Before sintering, moisture of mixtures was evaporated in the oven at the  $105^{\circ}\text{C}$ . The mixtures were moulded and sintered  $900^{\circ}\text{C}$  in the laboratory in the sintering oven. After the temperature had reached the required temperature, the briquettes were not left in the sintering oven and were put out. The briquettes were produced through this process conditions were tested for compressive strength according to the Turkish Standards (TS EN 771-1) [8].

### ш. Results and Discussion

### A. Characterization of BFS and S

To characterize the S and BFS, following experiments were carried out. Chemical analyses of the materials were given in Table 1. Content analyses of S sample were given in Table 2 and results are 6.4% sand, 34.6% silt and 59.0% clay. As it can be seen in Fig.1 particle size distribution of S sample was between 0.003-5.000mm, mean diameter of BFS was 7.48 $\mu$ m. In addition to the mentioned information, specific gravity of the BFS and S was 2.81g/cm³ and 2.75g/cm³ respectively.

TABLE I. CHEMICAL ANALYSES OF THE MATERIALS

Constituents (%)	S	GBFS
$SiO_2$	58.36	36.70
$Al_2O_3$	22.17	14.21
$Fe_2O_3$	7.09	0.98
CaO	2.61	32.61
MgO	2.46	10.12
$K_2O$	2.27	0.76
Na <sub>2</sub> O	0.71	0.42
$SO_3$	0.34	0.99
(LOI)	3.35	NA



TABLE II. CONTENT OF THE SOIL SAMPLE

Content	%w/w
Gravel	0.0
Sand	6.4
Silt	34.6
Clay	59.0

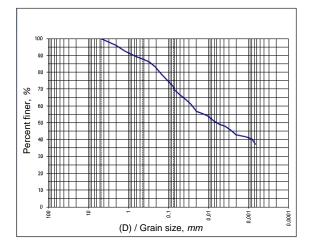


Figure 1. Grain size curve of the S.

To obtain thermal behavior of S, TG analysis was carried out and it was found that there was 10.6% weight loss totally. Moisture and water loss of soil were 2.9% up to 156°C. In the range between 156°C and 767°C, decomposition started and water loss of soil reached up 10.6%. As it can be seen in Fig.2 after the 767°C, decomposition continued.

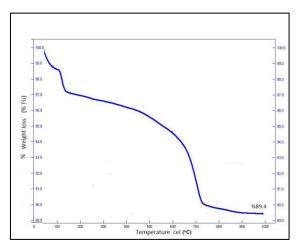


Figure 2. TG analysis of the BFS.

It can be seen in Fig.3, totally weight loss was 3.3%. Because of the high level calcium components, important chemical reactions occurred 600-800°C and exhaust gases emitted.

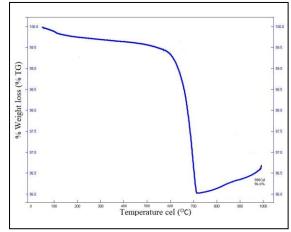


Figure 3. TG analysis of the BFS.

# B. Compressive strength values of briquettes

After sintering of the mixtures, compressive strength tests were applied to the briquettes. Compressive strength results of the briquettes are shown in Table 3. It is concluded that briquettes with compressive strength value of 39.4MPa can be produced at 900°C. This result was obtained briquette, which was prepared with BFS in ratio of 2% and this is the best of compressive strength result than that of prepared using other mixtures. This compressive strength result is very high value because Turkish Standard (TS EN 771-1) requires (9.8-23.54 MPa). In addition to these conclusions briquettes with BFS give more compressive strength value than that of non-additive.

TABLE III. MIXTURE RATIO AND COMPRESSIVE STRENGTH RESULTS OF THE BRIOUETTES

No	Mixtures (%)	Compressive strength (MPa)
1	100K	34.6
2	98K+2BFS	39.4
3	95K+5BFS	35.4
4	90K+10BFS	27.6
5	80K+20BFS	21.6

### **IV.** Conclusions

The following conclusions can be drawn from the experimental results. The briquette obtained from BFS in ratio of 2% gives better mechanical strength than that of prepared using other mixtures. This result is very important because BFS is an industrial waste and has higher compressive strength values than S at the same conditions. In addition to these results, all mixtures can be used according to relevant standards. This is very important result to contribute environmental pollution and decreasing of production costs.



### References

- M. Öner, K. Erdoğdu, and A. Günlü, "Effect of components fineness on strength of blast furnace slag cement" *Cement and Concrete Research*, vol.32, iss.4, 2002, pp. 463-469.
- [2] S. Ghosh, M. Das, S. Chakrabarti, and S. Ghatak, "Development of ceramics tiles from common clay and blast furnace slag" *Ceramics International*, vol.28, iss.4, 2002, pp. 393-400.
- [3] M. L. Öveçoğlu, S.Kınıkoğlu, and M.S. Taşar, "Development and characterization investigations of titania nucleated slag based glassceramics", *Turkish Ceramic Society Publication*, iss.5, 1992, pp.108-118.
- [4] A. A. Francis, "Conversion of blast furnace slag into new glass-ceramic material", *Journal of the European Ceramic Society*, vol.24, iss.9, 2004, pp.2819-2824.
- [5] E. Karamanova, G. Avdeev, and A. Karamanov, "Ceramics from blast furnace slag, kaolin and quartz", *Journal of the European Ceramic Society*, vol.31, iss.6, June 2011, pp.989-998.
- [6] E. M. Saucedo-Salazar, Y. A. Perera-Mercado, F. R. Rodríguez-Ruiz, and A. Arauza-Villarrea, "Production of glass spheres from blast furnace slags by a thermal flame projection process", *Ceramics International*, vol.40, iss.1, Part A, January 2014, pp.1177-1182.
- [7] K. Dana, J. Dey, and S. K. Das, "Synergistic effect of fly ash and blast furnace slag on the mechanical strength of traditional porcelain tiles", *Ceramics International*, vol.31, iss.1, 2005, pp.147-152.
- [8] Turkish Standards EN 771-1, "Specification for masonry units-Part 1: Clay masonry units", *Turkish Standards Institute*, Ankara, Turkey, 2005.

#### **About Authors:**

### Özlem Çelik Sola, Associate Professor, Ph.D

Dr. Özlem Çelik Sola received his BS degree from Istanbul Technical University, Turkey in 1991, and MS and PhD degrees from the Yıldız Technical University in 1999 and 2004, in Chemical Engineering. Since 1995, she has been served as a Research Assistant, Assist. Prof. Dr. and Assoc. Prof. Dr. at the Department of Civil Engineering, Istanbul University. Ozlem Celik currently working as a Associate Professor at Istanbul University.



Mrs. Çelik Sola completed her PhD on "The Utilization of Industrial Wastes in Building Sectors" from the Yıldız Technical University. Her research interests include; the management and utilization of industrial wastes within the construction industry and construction materials.

### Baris Savın, Ph.D

Dr. Baris Sayin is currently employed by Department of Construction and Technical Affairs at Istanbul University as a Civil Engineer. Mr. Sayin graduated from Istanbul University with BS, MS and PhD in Civil Engineering. During the graduate education, he worked as a Research Assistant in the Department of Civil Engineering at the University in between 2000 and 2009.



Mr. Sayin collaborated with Prof. Dr. Hamid
Saadatmanesh on insulated FRP-strengthened RC structures and FRPsandwich panels as a Visiting Scholar in the Department of Civil Engineering
and Engineering Mechanics at The University of Arizona for 12-months from
September 2012. His research areas are fiber composites, industrial wastes
and RC structures. He has published many articles regarding civil engineering.

